



## Kalrez® V-Rings for Oil Production Six-Year Service Record

The outstanding service record for Kalrez parts in oil production applications is best shown by the results of testing V-rings recovered after six years' service in a producing well. As shown in *Table 1* and *Figures 1–3*, except for a slight drop in hardness, the aged V-rings were indistinguishable in physical properties and appearance from the unaged control.

No competitive comparisons are made in this technical information because only Kalrez V-rings are suitable for service conditions this severe.

*Figure 1. This Kalrez V-ring was essentially unaffected by six years downhole.*




**Table 1**  
**Kalrez V-Rings: Six-Year Service Record**

Conditions	Production	
Depth, 4,602 m (15,100 ft)	3,000 BBL/Day Oil	
Temperature, 149°C (300°F)	125 BBL/Day Water	
Pressure, 46.2 MPa (6,700 psi)	Gas/Oil Ratio—1.3	
Physical Property Comparisons (Kalrez 3065 Compound)		
	New V-Rings	Six-Year Downhole V-Rings
Tensile at Break, MPa (psi)	20.7 (3,010)	21.5 (3,120)
Elongation, %	27	30
Hardness, Shore A	95	85

*Figure 2. Tubing-to-packer seal after six years downhole*



*Figure 3. Close-up of Figure 2*

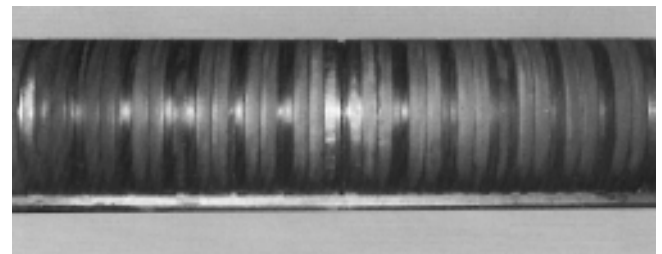

---

For more information on Kalrez®  
or other elastomers:

(800) 853-5515 (U.S. & Canada)  
(302) 792-4000  
[www.dupont-dow.com](http://www.dupont-dow.com)

---

Global Headquarters  
DuPont Dow Elastomers L.L.C.  
300 Bellevue Parkway, Suite 300  
Wilmington, DE 19809 USA  
Tel. 302-792-4000  
Fax. 302-892-7390

European Regional  
Headquarters  
DuPont Dow Elastomers S.A.  
2, chemin du Pavillon  
CH-1218 Le Grand-Saconnex  
Geneva, Switzerland  
Tel. 41-22-717-4000  
Fax. 41-22-717-4001

Asia Pacific Regional  
Headquarters  
DuPont Dow Elastomers Pte Ltd.  
1 Maritime Square #10-54  
World Trade Centre  
Singapore 099253  
Tel. +65-275-9383  
Fax. +65-275-9395

South & Central  
America Regional  
Headquarters  
DuPont Dow Elastomers Ltda.  
Rua Henrique Monteiro, 90  
5: andar – Pinheiros  
05423-912  
São Paulo – SP  
Brazil  
Tel. +55-11-816-0256  
Fax. +55-11-814-6845

Kalrez Asia Parts  
Marketing  
DuPont Dow Elastomers Limited  
19-2 Kiyohara Kogyo-Danchi  
Utsunomiya-Shi Tochigi  
Prefecture 321-32  
Japan  
Fax. 81-28-667-9670

Kalrez Parts Marketing  
DuPont Dow Elastomers L.L.C.  
P.O. Box 6098  
Newark, DE 19714  
Tel. 800-323-9806

Kalrez European Parts  
Marketing  
DuPont Dow Elastomers N.V.  
Antoon Spinoystraat 6  
B-2800 Mechelen  
Belgium  
Fax. 32-15-44-1790

---

The information set forth herein is furnished free of charge and is based on technical data that DuPont Dow Elastomers believes to be reliable. It is intended for use by persons having technical skill, at their own discretion and risk. The handling precaution information contained herein is given with the understanding that those using it will satisfy themselves that their particular conditions of use present no health or safety hazards. Because conditions of product use and disposal are outside our control, we make no warranties, express or implied, and assume no liability in connection with any use of this information. As with any material, evaluation of any compound under end-use conditions prior to specification is essential. Nothing herein is to be taken as a license to operate under or a recommendation to infringe on any patents.

**CAUTION:** Do not use in medical applications involving permanent implantation in the human body. For other medical applications, discuss with your DuPont Dow Elastomers customer service representative.

Kalrez® is a registered trademark of DuPont Dow Elastomers.

Copyright © 1997 DuPont Dow Elastomers.  
All Rights Reserved.

